



U.S. Department of Energy  
Energy Efficiency and Renewable Energy

# **Wear Resistant AlMgB<sub>14</sub> Composites**

**Crosscutting Applications of a New Class of Ultra-Hard Materials  
#1789**

**B. A. Cook, A. M. Russell, J. L. Harringa, and J. P. Peters**

**Materials and Engineering Physics Program  
Ames Laboratory  
and  
Department of Materials Science & Engineering  
Iowa State University  
Ames, IA 50011-3020**

**EERE ITP Program Review  
June 2, 2005  
Chicago, IL**



**IOWA STATE UNIVERSITY**



# Organization

- **Project Summary**
- **Brief Background**
  - (the importance of microstructure)
- **Erosion & Abrasion testing**
  - (recent milestones)
- **Modeling**
- **Commercialization**
- **Future Plans**



## Crosscutting Applications for a New Class of Ultra-Hard Borides (#1789)

**Goal:** increase U.S. industrial energy efficiency through development of advanced, wear-resistant materials

**Challenge:** monolithic ceramics wear by brittle fracture; metals wear by plastic deformation. Neither possesses extreme resistance to tribological wear across a broad range of conditions; wear resistance has been limited by available materials and microstructures.

**Benefits:** extended lifetime of critical pump, valve, and material transport components; increased efficiency in mining and metal removal operations. energy savings of 5.6 trillion Btu/yr by 2020; 26 trillion Btu/yr by 2030.

**Potential End-User Applications:** abrasive water-jet cutting nozzles, material conveying system liners (particularly bends and elbows), valves, seals, and bearings; cutting and milling inserts, extrusion and drawing dies; low-friction coatings for MEMS and other rotating/sliding components

**FY06 Activities:** optimize processing technology and process scale-up, continue microstructural refinement, advance theoretical modeling efforts to enable accurate prediction of best composition and microstructure for each application, establish industry-wide consensus on performance of superior wear resistant compositions; re-tool commercialization infrastructure


**Participants:** (primary) Kennametal Advanced Solutions Group, IMI Vision, Inc., University of Missouri-Rolla High Pressure Waterjet Laboratory

(secondary) Praxair Surface Technology, Inc, Norton St. Gobain, Ceracon, CeramTec, Concurrent Technologies, Inc. Harris Corp., Sunnen Corp., Engis Corp.




# Crosscutting Applications for a New Class of Ultra-Hard Borides (#1789)

## Erosion-resistance Applications:

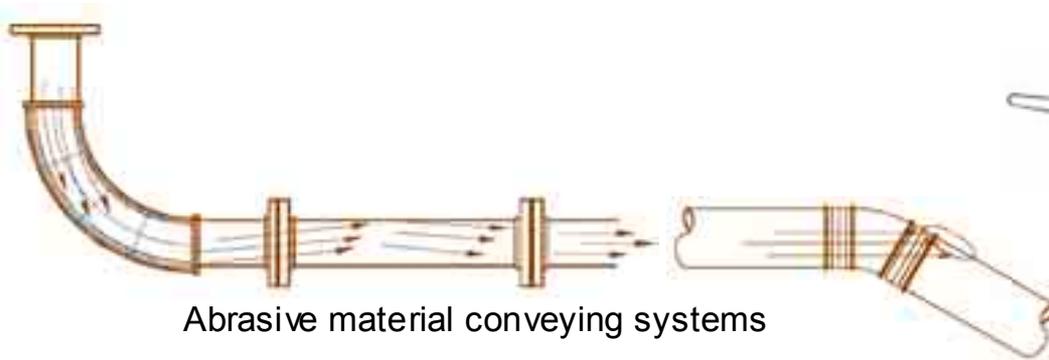



Abrasive material conveying systems

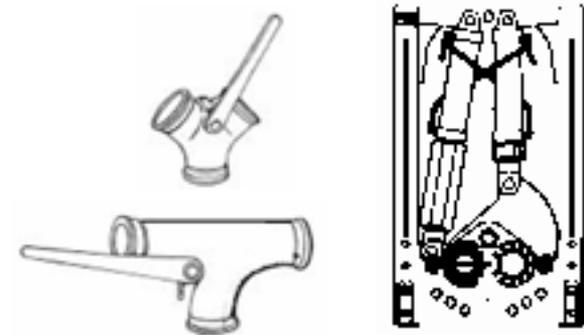

Diversion valve systems



Pump components (shaft seals, impellers, linings)

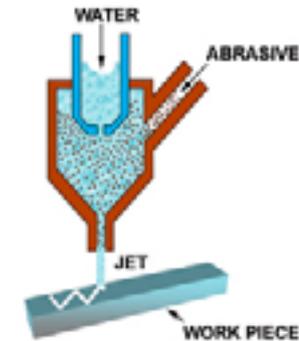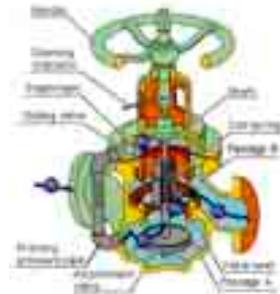


Abrasive water jet nozzles



## Background:

- **Exploratory work began in 2001 on high-hardness borides**
  - Discovered relationship between unit cell occupancy and Fermi energy in single phase  $\text{AlMgB}_{14}$
- **Observed microhardness values of 35 GPa in  $\text{AlMgB}_{14}+\text{Si}$  polycrystalline samples**
  - Higher hardness in  $\text{AlMgB}_{14}+\text{TiB}_2$  composites (45+ GPa)
- **Examined role of dopants vs. second phase additives**
- **Performed preliminary lathe cutting tests using hot pressed inserts**
- **Wear resistance unknown until 2004**

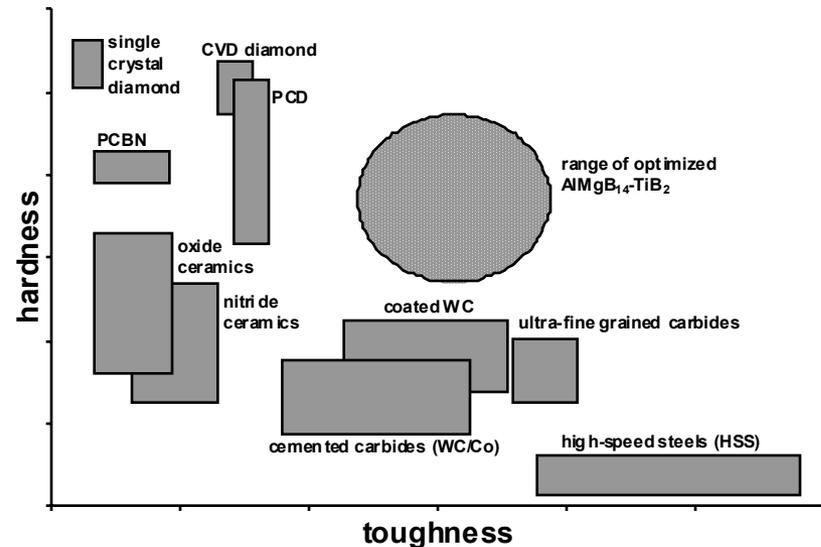

*N.B., hardness alone does not guarantee good wear resistance...*




# “BAM” $\neq$ $\text{AlMgB}_{14}$

- Maximum hardness of (single phase)  $\text{AlMgB}_{14}$  ~ 30-35 GPa

Higher hardness requires *microstructural engineering*:



Composition	Microhardness, $\text{HV}_{0.1}$ , GPa	Wear Coefficient ( $\text{m}^2/\text{N} \times 10^{-15}$ )
$\text{AlMgB}_{14}$	32	1.6
$\text{Al}_2\text{O}_3\text{-TiC}$	22	2.9
$\text{Al}_2\text{O}_3\text{-SiC}_w\text{-TiC}$	19	2.7
WC/Co	23	1.8

Bhat, Deepak G.; Bedekar, Vikram A.; Batzer, Stephen A., "A Preliminary Study of Chemical Solubility of Ultra-Hard Ceramic  $\text{AlMgB}_{14}$  in Titanium: Reconciliation of Model with Experiment," *Machining Science and Technology* 8(3) (2004), 341-355.

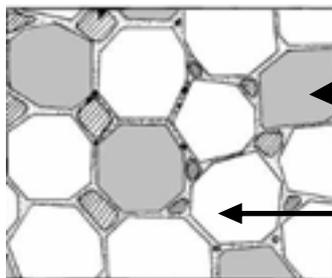

$\text{TiB}_2$ -rich region

$\text{AlMgB}_{14}$ -rich region

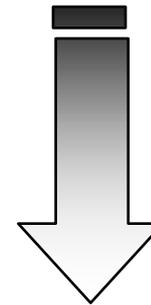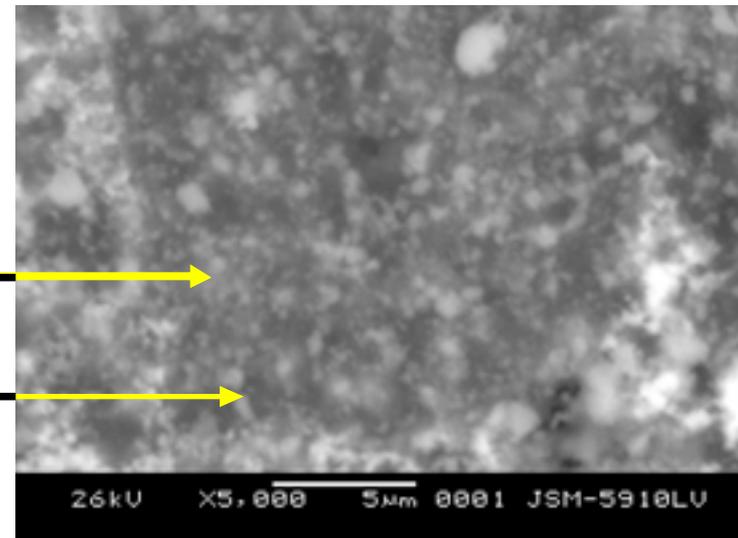



# Wear resistance:

**Objective: Combat energy losses due to material degradation by development of new, wear-resistant materials**

“wear” encompasses a number of distinct physical mechanisms

- Abrasive and erosive wear are functions of hardness **AND** fracture toughness:

$$V = cK_{1c}^m H_v^n$$

V = volume removed/impact


$K_{1c}$  = fracture toughness

$H_v$  = hardness

$m \cong -1.3$

$n \cong -0.5$


C = proportionality constant

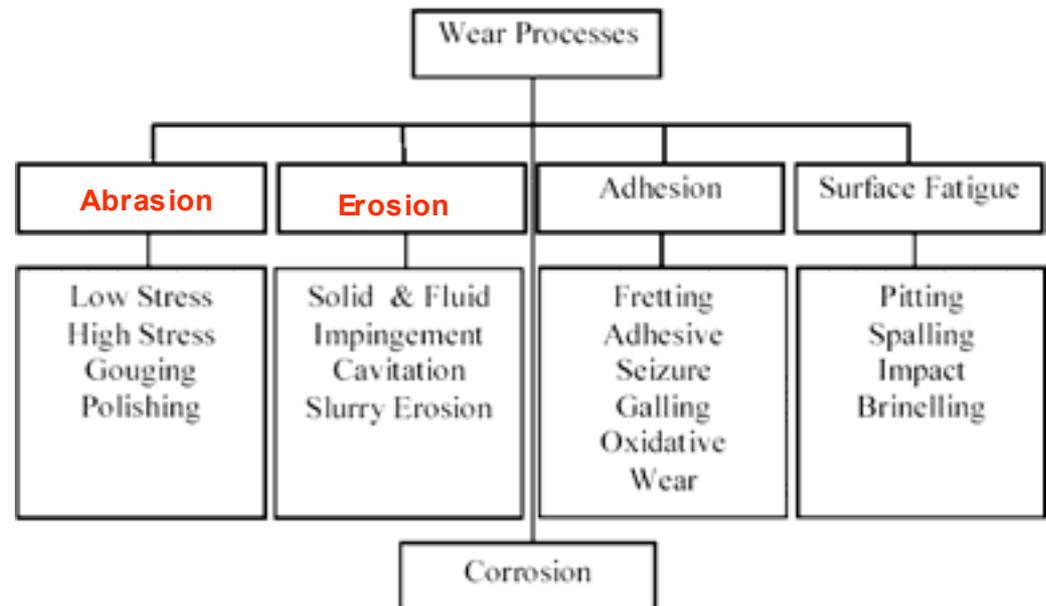




# Erosion resistance: relative wear volume

60 sec erosion with 100 m/s  $Al_2O_3$

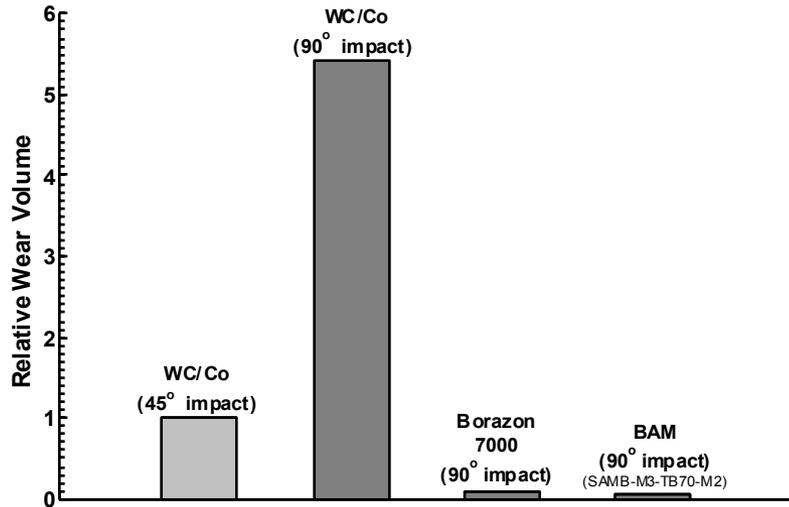

Effect of impingement angle (WC/Co)



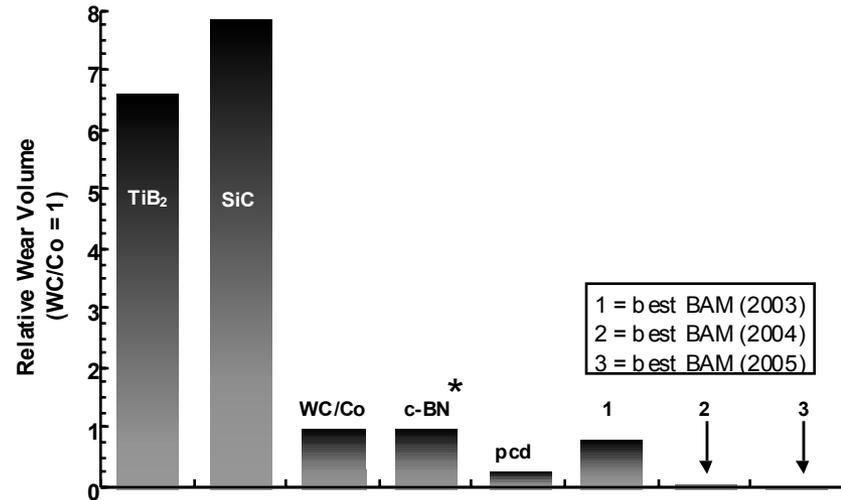


Comparison with other materials

\* "standard grade" CBN




# Steady state erosion:

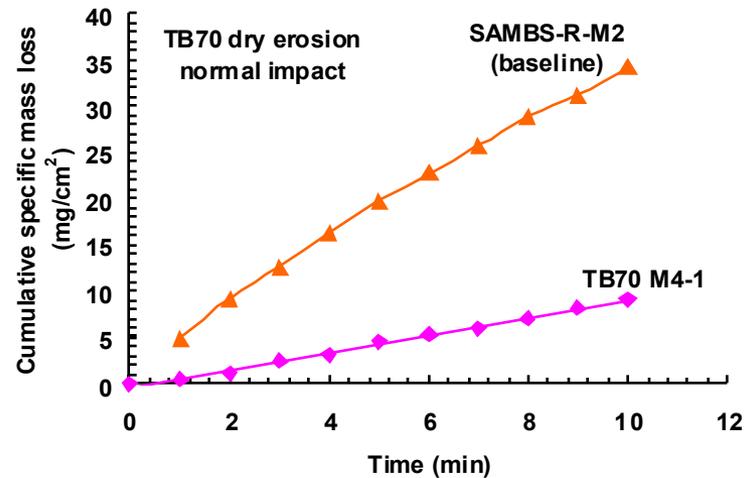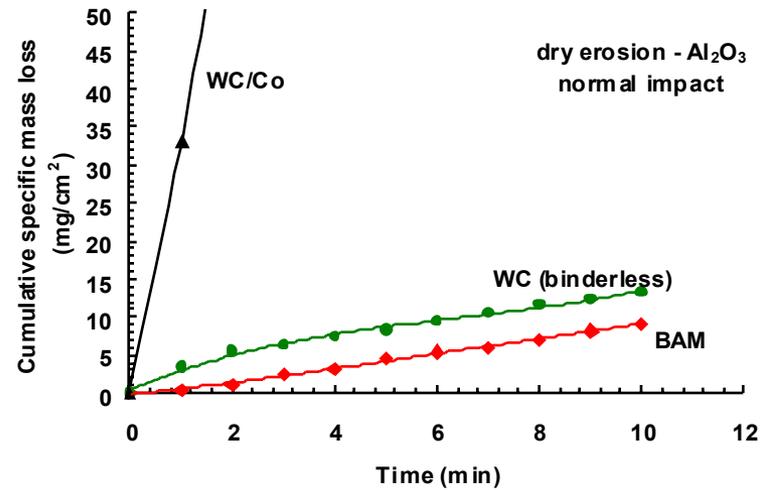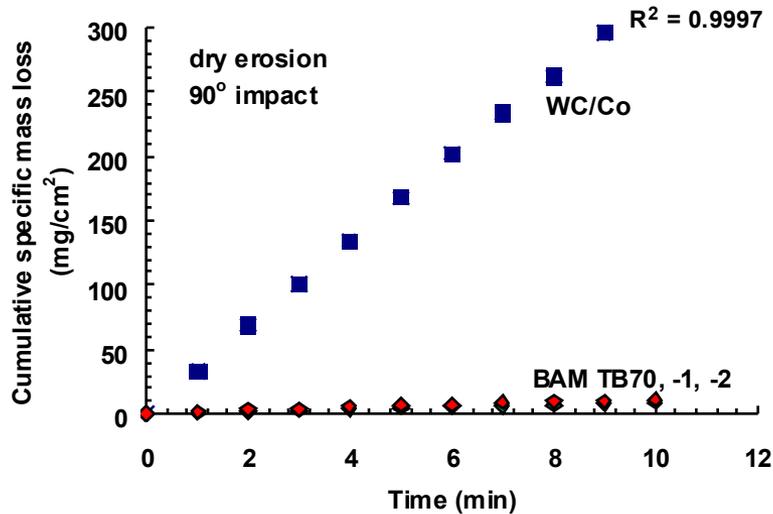






# Diamond belt abrasion test:

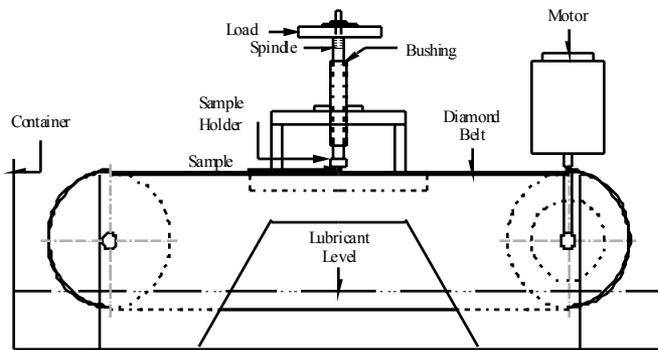


Variation in abrasive wear rate with applied loading at a constant speed of 65 m/min

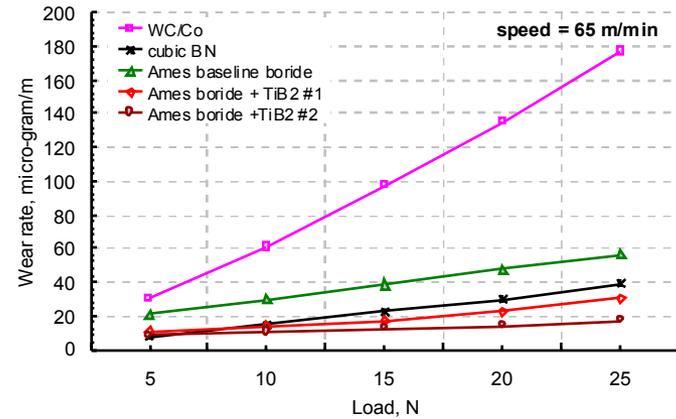

Variation in wear rate with speed at a constant 20N loading

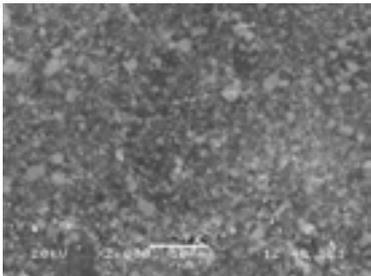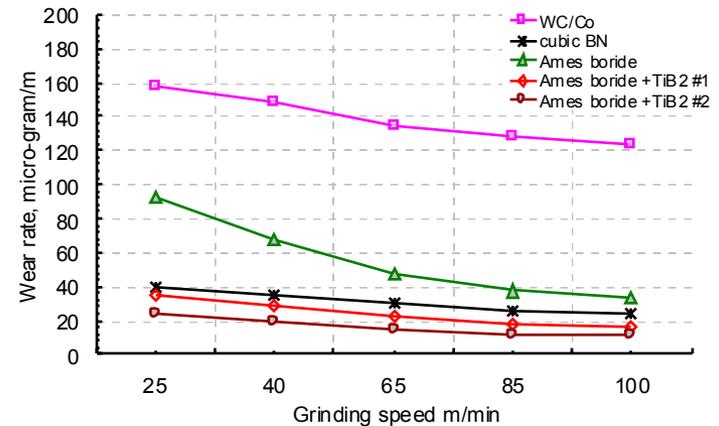

5 N load + 0.42 m/s belt speed

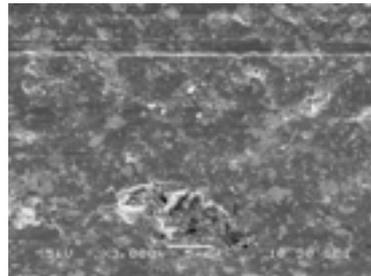


20 N load + 1.67 m/s belt speed



## Proposed damage mechanism:

TB70-M3 5 seconds at 45° impact angle

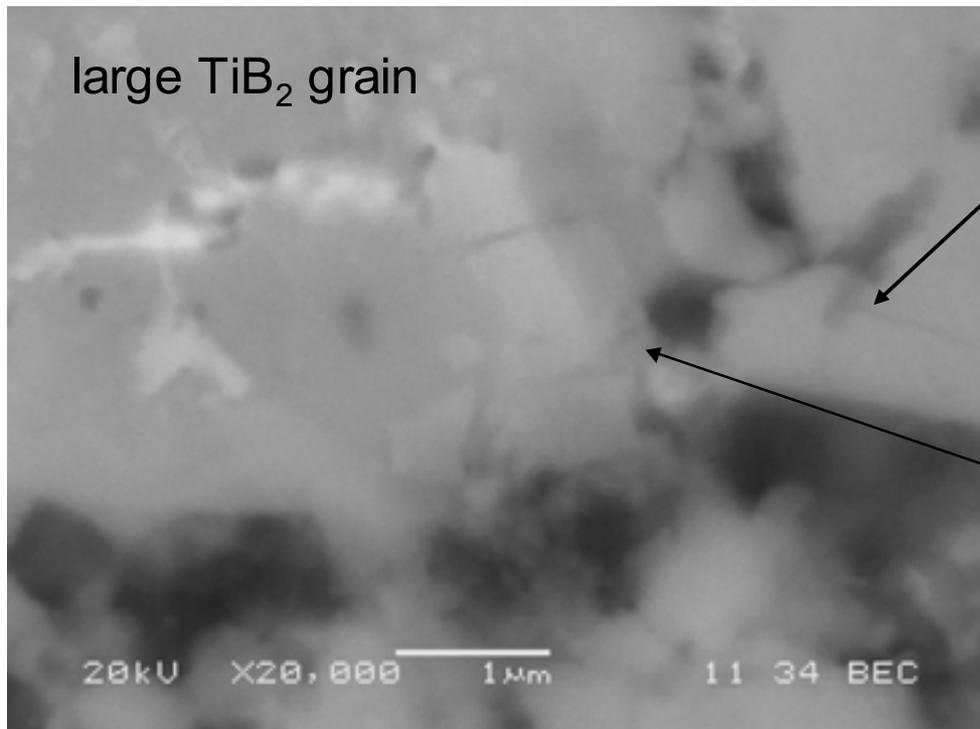

Transgranular  
cracks in  $\text{TiB}_2$


Crack arrest at  $\text{TiB}_2$  -  
 $\text{AlMgB}_{14}$  interface



# Lathe cutting tests:

Workpiece material: Ti-6Al-4V

Comparison of nose wear in different tool materials after machining tests

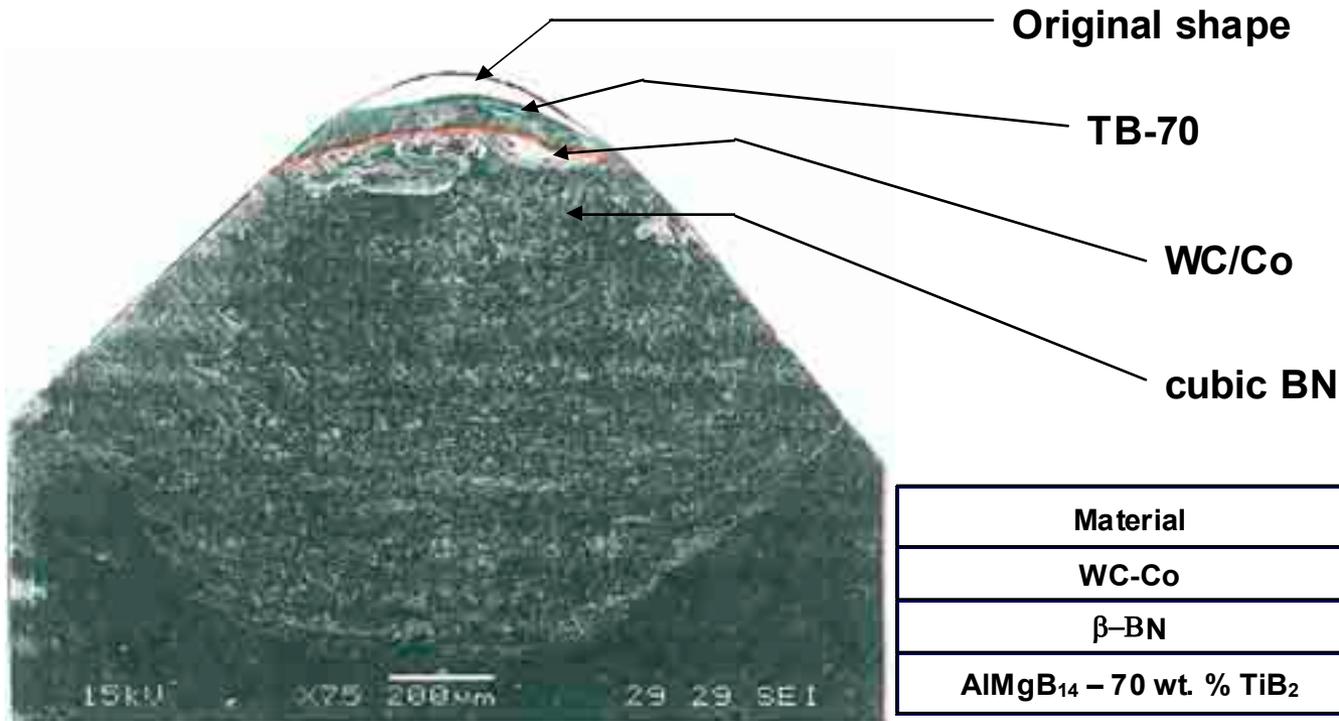




## Theoretical modeling:

Wear of composites was simulated by a “micro-scale dynamic model.”

Objective: to understand the relationship between microstructure and wear:

- Volume fraction of reinforcement
- Size and size distribution of reinforcement
- Abrasive grit size

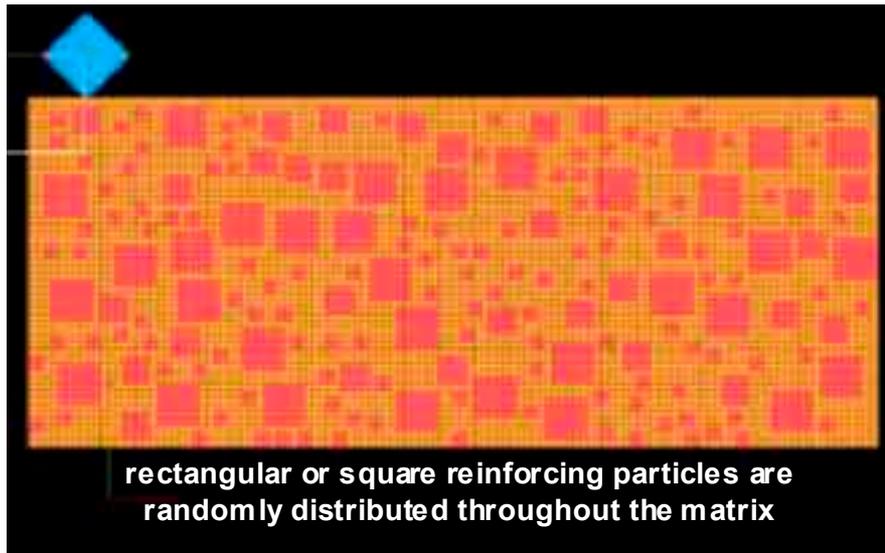

“micro-scale dynamic model:”

- Discretize composite and erodent
- Define small volume of material
- Connect volume elements by springs  
(incorporate Young's modulus, yield strength, tensile strength; estimate interfacial bonding strength)
- Calculate force coefficients for each volume element  
(Newton's 2nd law)
- Calculate total force on each site
- Calculate new velocity of each site
- Calculate deformation of bonds
- If deformation > critical value (i.e., fracture strain of material), then bond is broken and fracture is nucleated

J. Hu, D. Y. Li, and R. Llewellyn

“Computational investigation of microstructural effects on abrasive wear of composite materials  
Wear (2005) (in press)





# Predictions of model:


## Effect of reinforcement volume fraction

Model predicts existence of a critical volume fraction of reinforcement


- varies with material
- increases with increased bond strength between reinforcement and matrix

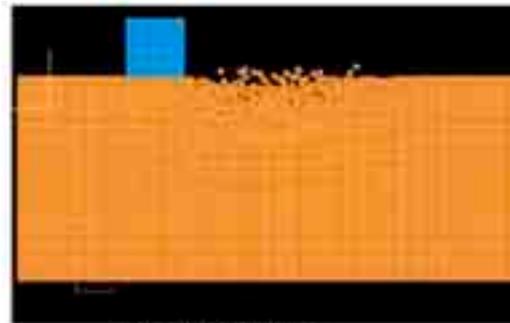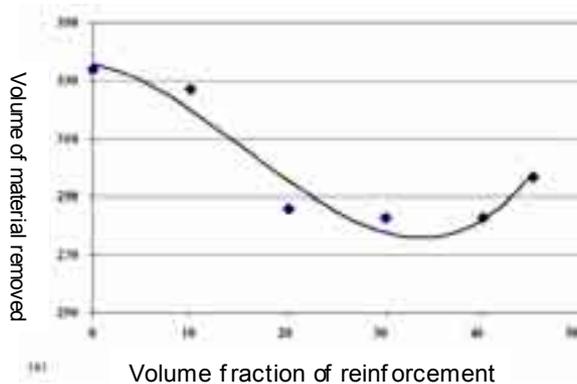


0% reinforcement

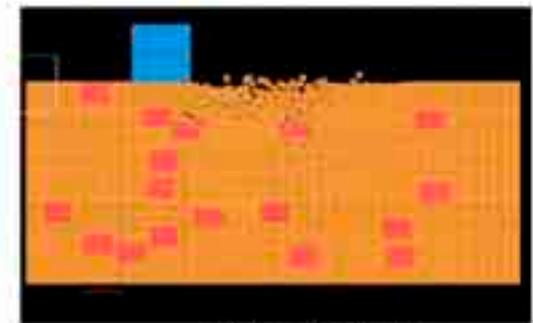

10% reinforcement

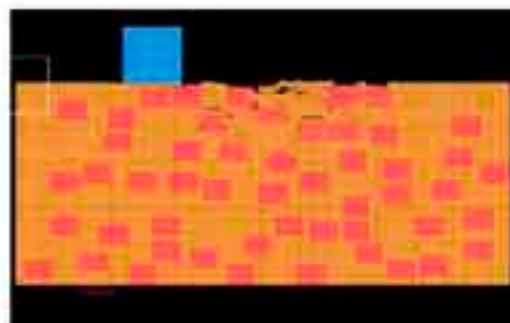

30% reinforcement

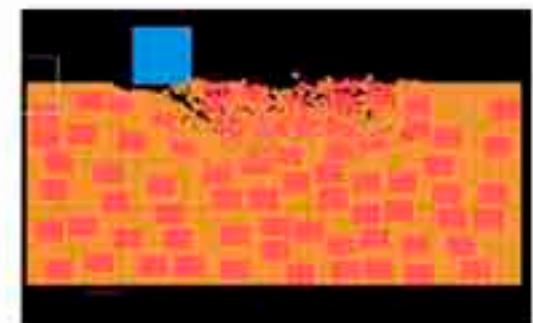


40% reinforcement




## Predictions of model:

### Effect of reinforcement distribution

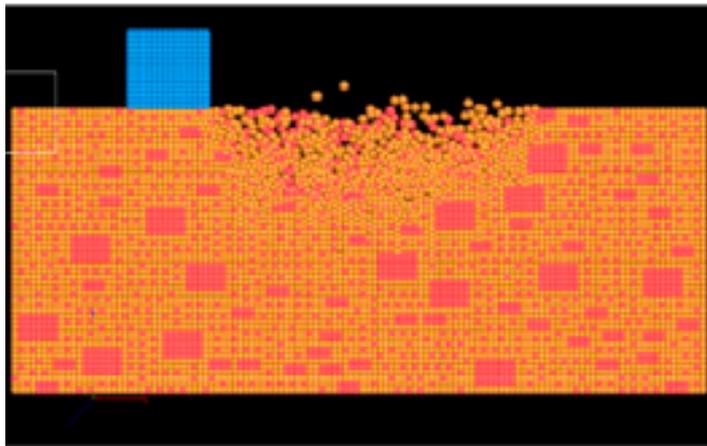

8% large+8% middle+19% small

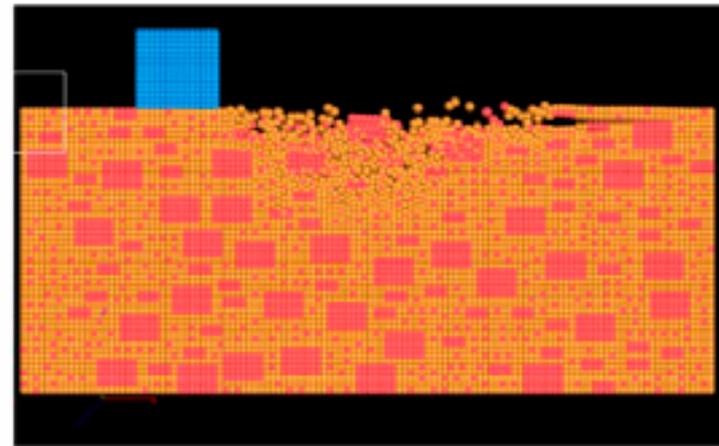

19% large+8% middle+8% small

Volume fraction held constant at 35%


Model predicts

- Distribution of sizes leads to higher wear resistance than monosized reinforcement



# Ultra-Hard Boride Technology Maturation via Stage-Gate

## Project milestones and stage-gates

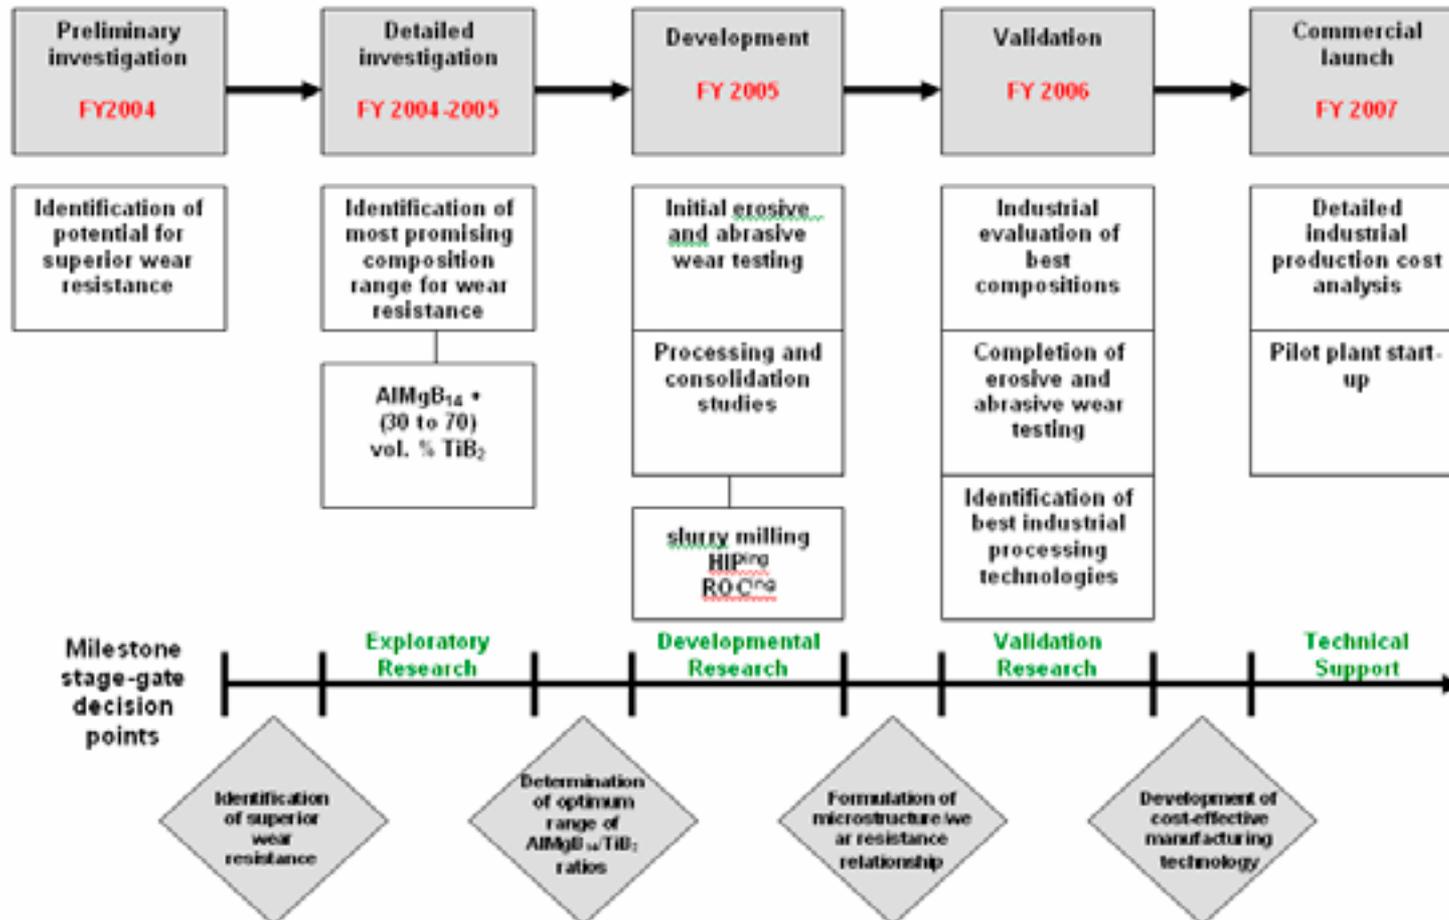



# Commercialization


$$N_c = N_i \times f_w \times f_d \times f_p \times f_s \times f_l \times f_a \times f_v$$

$N_c$  = # successfully commercialized laboratory technologies

$N_i$  = # of "good" ideas

- $f_w$  = fraction that actually "work"
- $f_d$  = fraction of ideas that are disclosed
- $f_p$  = fraction that are patentable
- $f_s$  = fraction that are "scalable"
- $f_l$  = fraction that are licensed
- $f_a$  = fraction that attract attention from investors
- $f_v$  = fraction that survive the "valley of death"

w/o ITP	with ITP
$f_w \sim 0.50$	$f_w \sim 0.50$
$f_d \sim 0.75$	$f_d \sim 0.75$
$f_p \sim 0.75$	$f_p \sim 0.75$
$f_s \sim 0.50$	$f_s \sim 0.50$
$f_l \sim 0.40$	$f_l \sim 0.60$
$f_a \sim 0.40$	$f_a \sim 0.60$
$f_v \sim 0.05$	$f_v \sim 0.50$

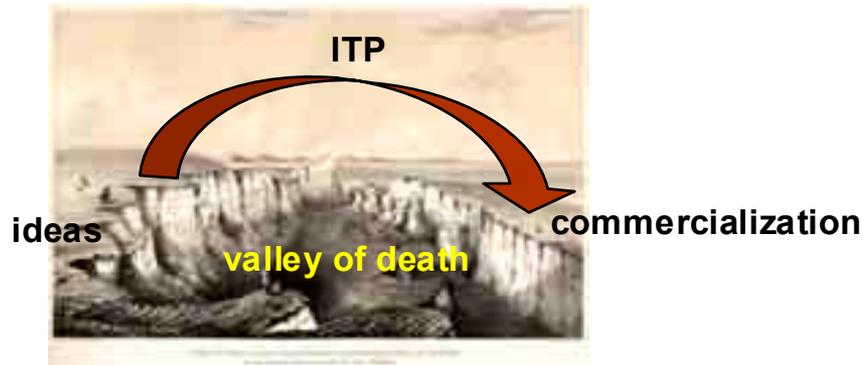

$$N_c \approx 0.001 N_i \text{ w/o ITP}$$


$$N_c \approx 0.025 N_i \text{ with ITP}$$

$$N_c^{w/ITP} \approx 25 N_c^{w/oITP}$$



## Commercialization...

Status as of 1 January, 2005

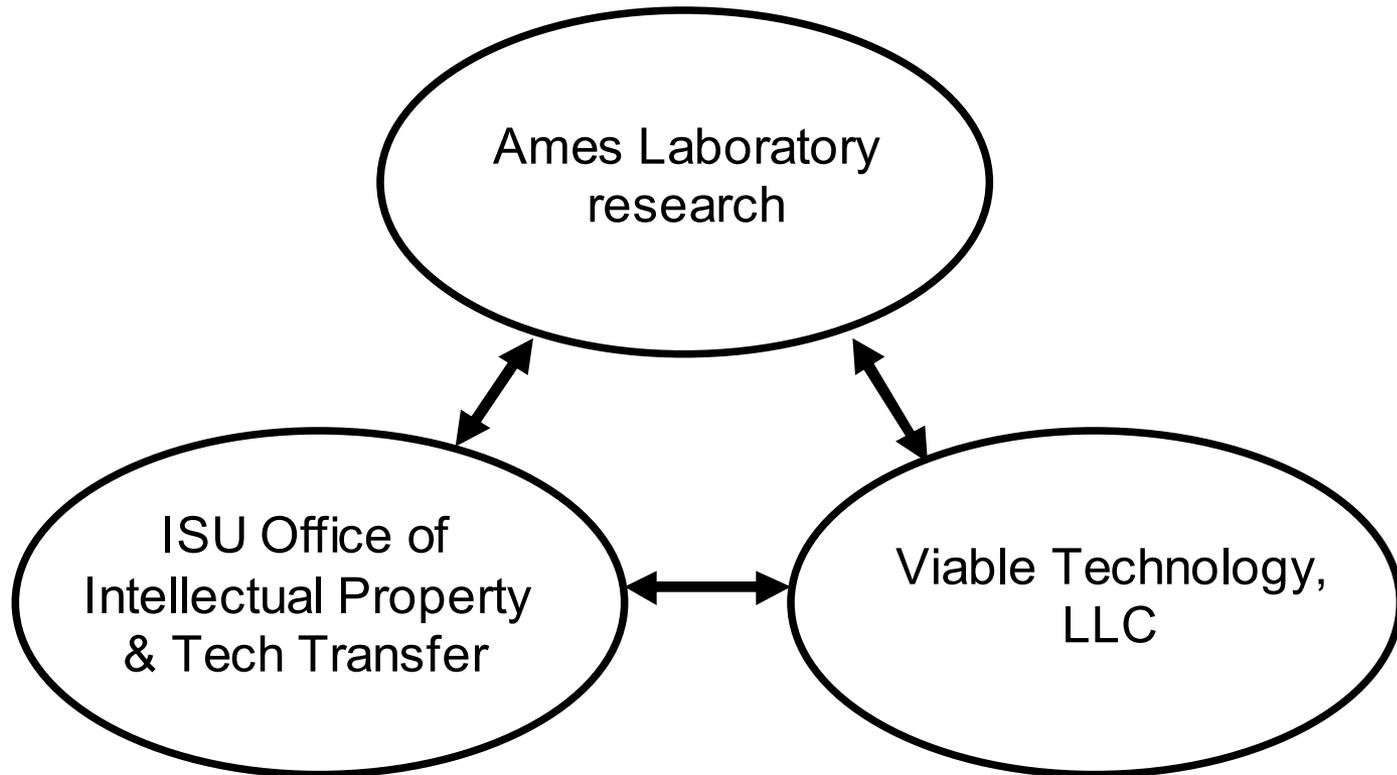



## Commercialization...

Status as of 1 May, 2005

*General consensus that Viable Tech lacked sufficient...*

- *Experience*
- *Facilities*
- *Capital*

License surrendered by Viable on March 31, 2005 to ISU's OIPTT

- OIPTT currently negotiating terms of *due diligence* from interested parties
- New licensing agreement expected to be in-place by Fall, 2005

Scale-up and commercialization of a complex materials-related technology imposes significant demands on the commercialization entity

*must possess sufficient resources to bridge the Valley of*

*Death*



## Commercialization...

### Risks / Variables (and Lessons Learned):

Resources (and background) of licensee

Exclusive license vs. non-exclusive license

Communication of expectations between participants

*Public sector support tends to be technology driven; private sector interest is market driven. □*

Assertiveness of the inventor/researcher in establishing / defining terms of licensing agreements

**Licensing ≠ commercialization!!!!**



## Plans for FY'06...

- **Research:**
  - Processing technology / scale-up
  - Microstructural refinement
  - Thin film technology – start with PLD; advance to magnetron sputtering
  - Modeling - enable accurate prediction of best composition and microstructure for each application
- **Industrial out-reach / collaboration:**
  - establish industry-wide consensus on performance of superior wear resistant compositions
- **Commercialization:**
  - Patent protection on wear resistant compositions (and related materials)
  - Re-tool “commercialization infrastructure”
  - Have processing partner on-board and ready to manufacture “pilot-plant” scale quantities by end of FY'06



**Additional slides...**






## Erosive wear:

Erosive wear is the loss of material from a solid surface by impingement from abrasive particles contained within a fluid

### Erosive wear depends on:

- hardness of erodent
- morphology of erodent
- hardness of target
- fracture toughness (ductility) of target
- impact velocity
- impact angle
- temperature
- duration of exposure to erodent

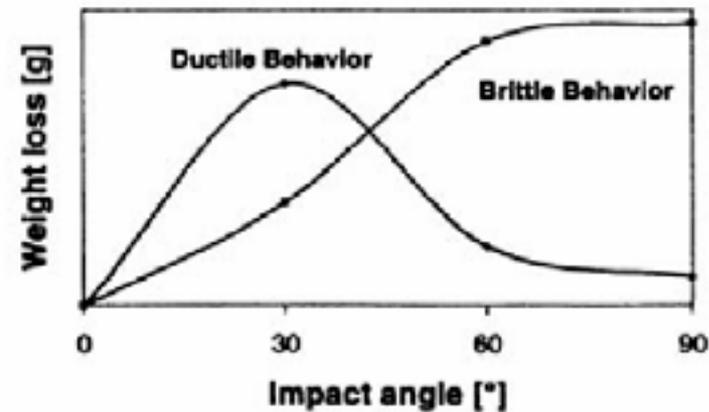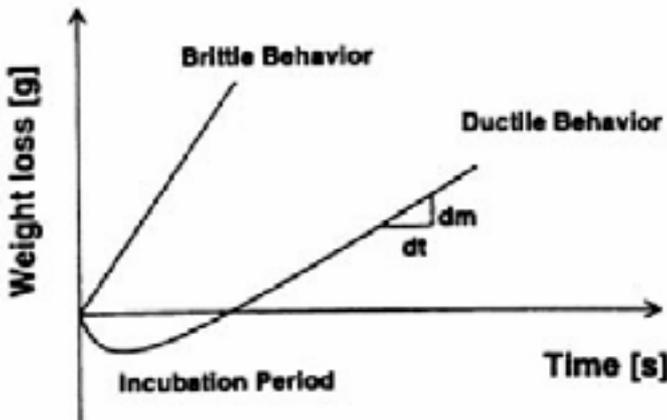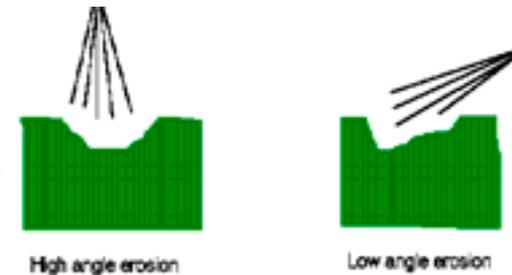


**Ductile metals behave qualitatively different than brittle ceramics**



# Erosion resistance test parameters:

## Erosive wear test parameters


<b>Erodent</b>	<b>Al<sub>2</sub>O<sub>3</sub></b>
<b>Ave. erodent particle size</b>	<b>100 – 200 microns</b>
<b>Hardness of erodent</b>	<b>20 GPa</b>
<b>Elastic modulus of erodent</b>	<b>375 GPa</b>
<b>Particulate velocity</b>	<b>~ 100 m/s</b>
<b>Nozzle diameter</b>	<b>10.4 mm</b>
<b>Nozzle length</b>	<b>80.2 mm</b>
<b>Stand-off distance</b>	<b>1 inch (25.4 mm)</b>
<b>Erosion angles</b>	<b>45° and 90°</b>
<b>Target</b>	<b>Hot pressed “BAM” coupons</b>

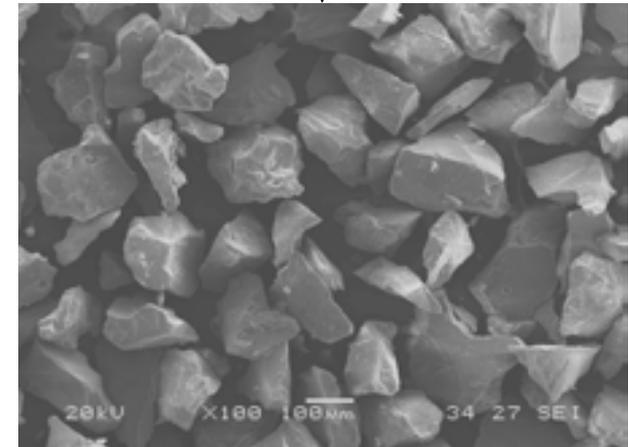




## Microstructural damage (5 sec at 45°):

WC/Co

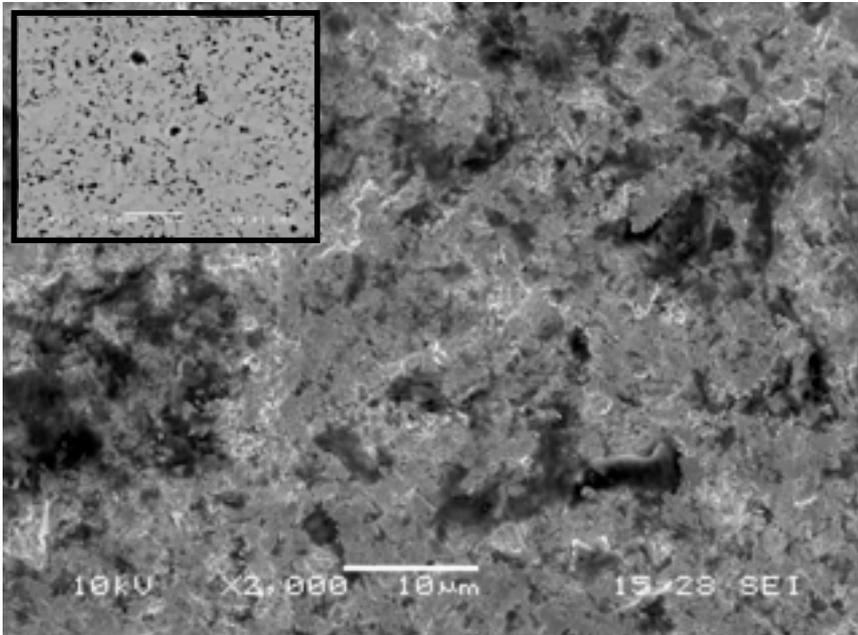

Removal of Co binder  
Large-scale ejection of WC grains

BAM (TB70-M2)

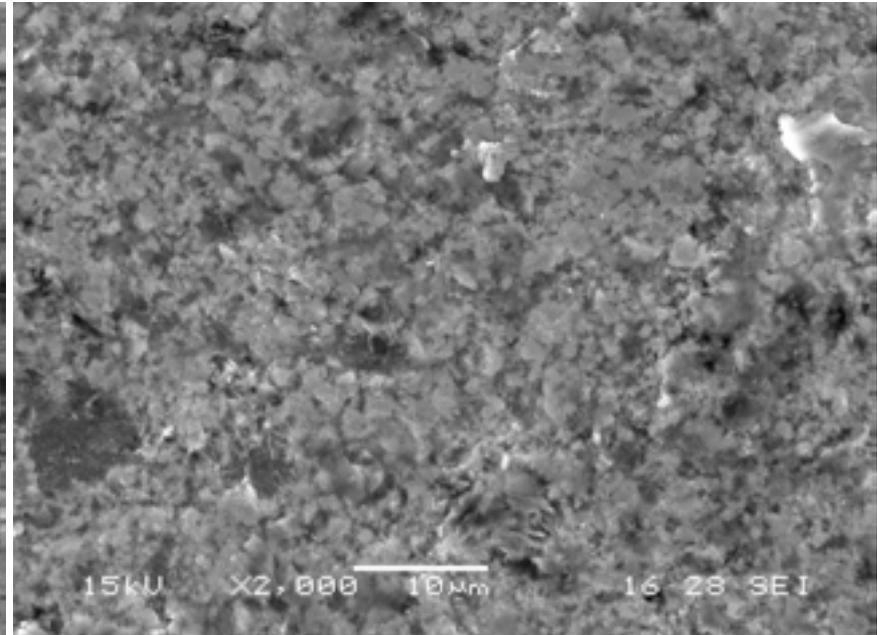


Minimal grain ejection  
No evidence of transgranular fracture




## Microstructural damage (5 sec at 45°):

WC/Co - before erosion

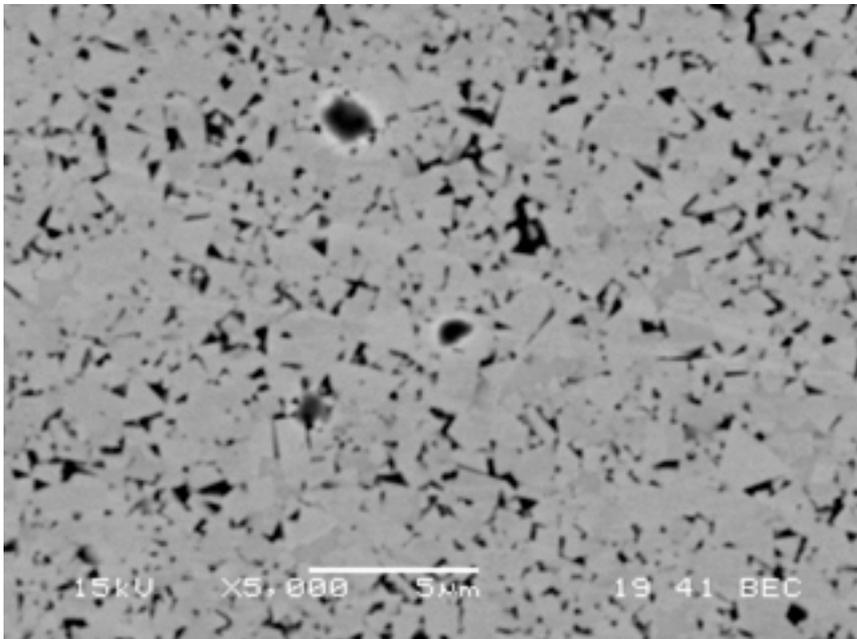

2 - 5 micron WC grains

WC/Co - after erosion

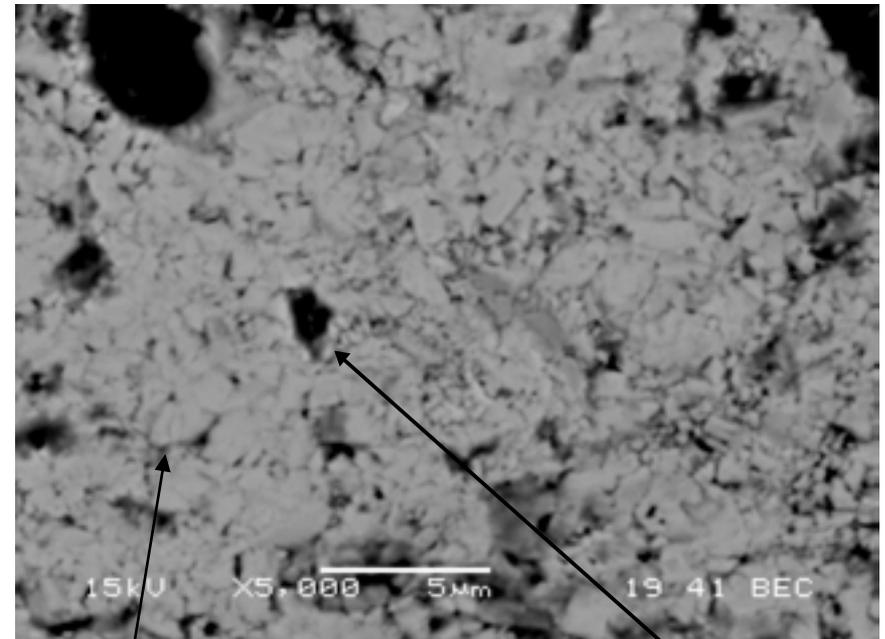


Transgranular fracture,  
grain ejection



# Microstructural damage (2 minutes at 45°):


C-BN

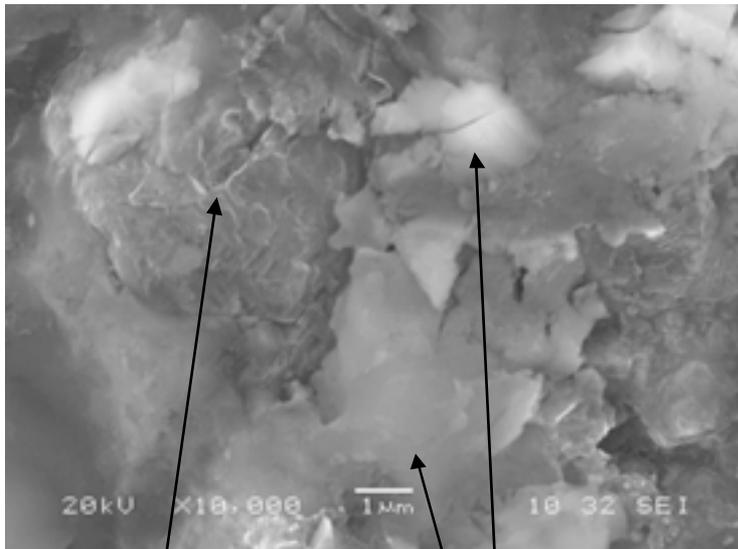

Transgranular fracture





BAM (TB70-M2)

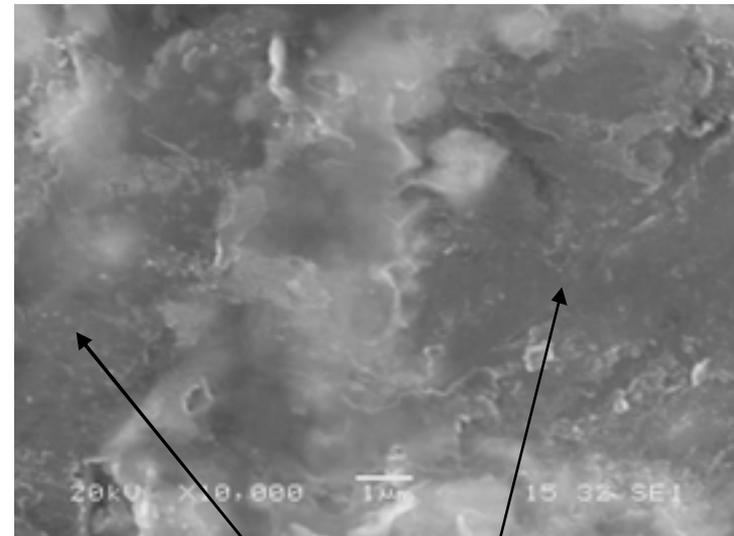

Few fractures; relatively smooth surface



## Thermal effects (2 minutes at 45°):

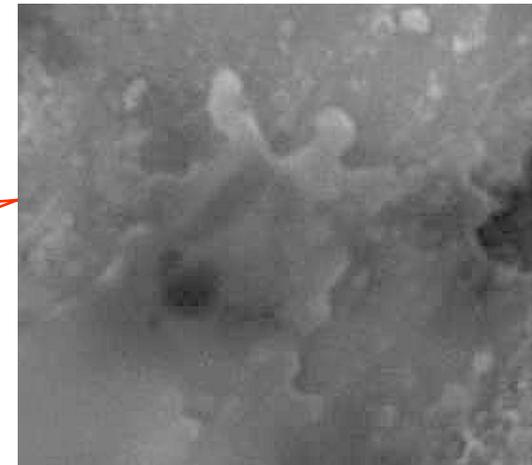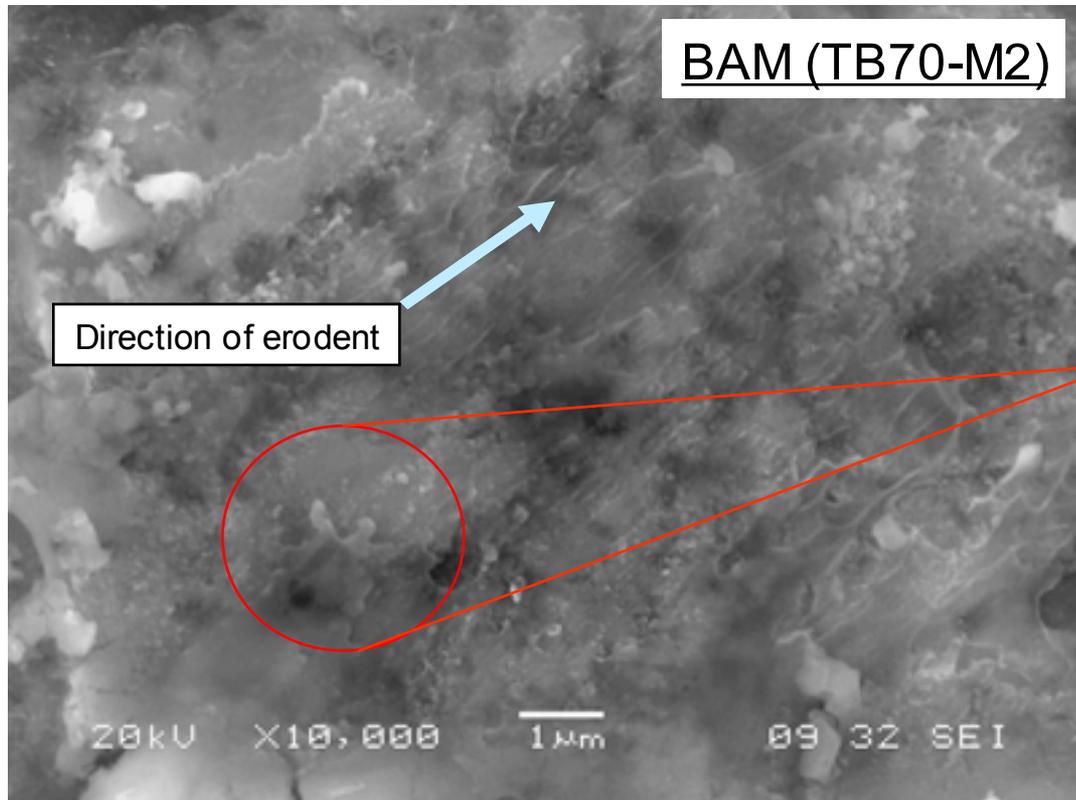

$B_2O_3$  melts at  $\sim 450^\circ C$

Note presence of droplets - possible formation of molten  $B_2O_3$



## Thermal effects:

### Model impact of erodent as an adiabatic indentation

Work performed in plastic deformation = localized heat absorbed by material

$$fP\delta z = mc\Delta T$$

where

P = impact load

$\delta z$  = penetration depth

m = mass

c = heat capacity

$\Delta T$  = local temperature increase

f = fraction of indentation energy  
dissipated within plastic zone

#### Values used in model:

hardness = 40 GPa


pyramid angle =  $74^\circ$

density =  $3.3 \text{ g/cm}^3$

heat capacity =  $1026 \text{ J/kg-K}$  (boron)

f = 0.4 (40% energy dissipated as heat)


b (plastic zone radius) = 20 microns

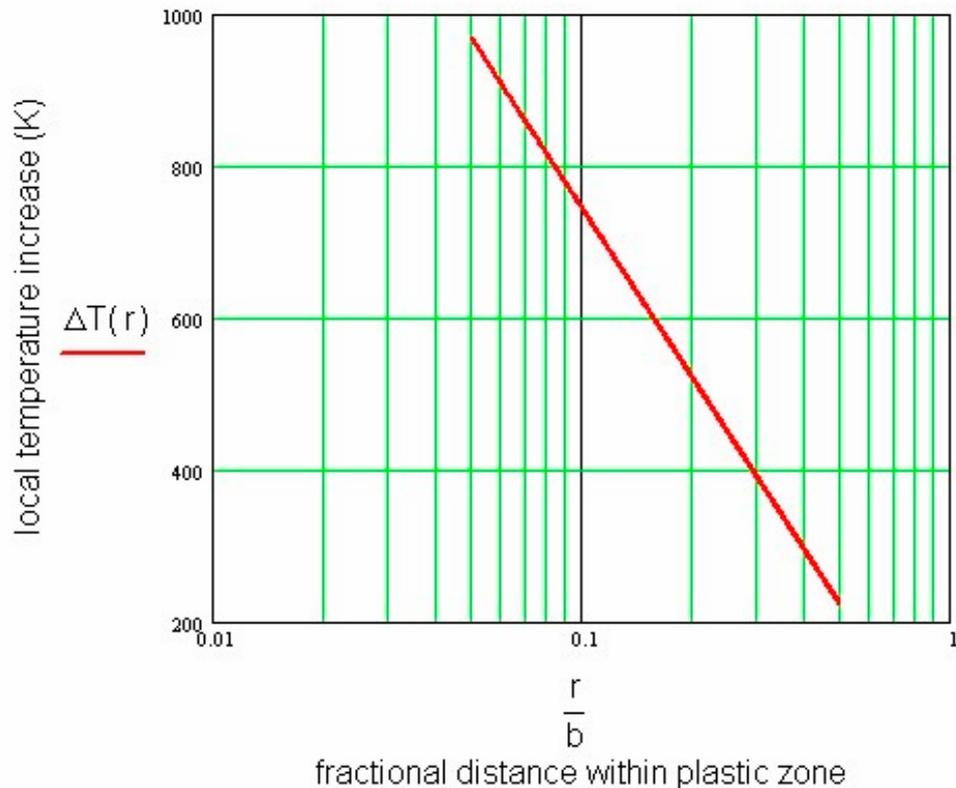




# Lathe cutting tests:

Workpiece: Ti-6Al-4V

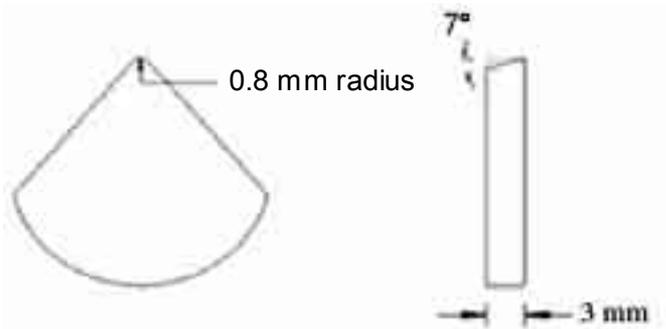


- relief angle =  $7^\circ$
- no chip breaker
- insert was glued and clamped to a tool holder
- depth of cut = 0.5 mm
- feed rate = 0.25 mm/rev
- cutting speed = 25 m/min
- turning performed on 38 mm diameter rod
- unlubricated (dry) cutting
- ISO 3685-1977 (International Standard for 'Tool-life Testing for Single Point Turning Tools')
- tool wear for one pass over a length of 200 mm measured to a resolution of  $1\ \mu\text{m}$  using a Toolmaker's microscope


WC/Co

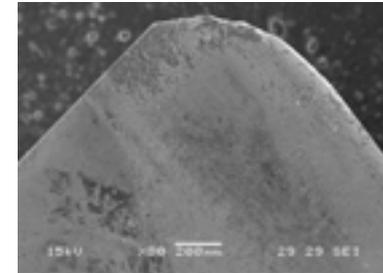

CBN

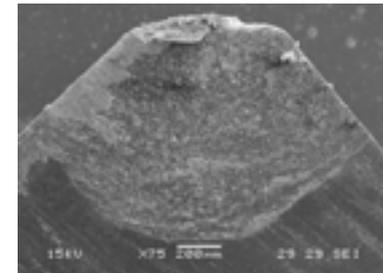

TB-70

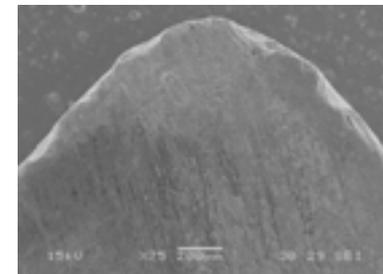



## Commercialization


**“...the new generation of clean energy entrepreneurial firms is finding it very difficult to make the leap from public sector funding for their innovations. Without new capital, many of our nation’s most promising energy entrepreneurs will fail.”**

*L. Murphy and P. Edwards, “Bridging the Valley of Death,” TechComm – The National Journal of Technology Commercialization, June-July (2004) p. 25.*




## Other promising technologies and applications...

In-situ Aluminum reinforcement

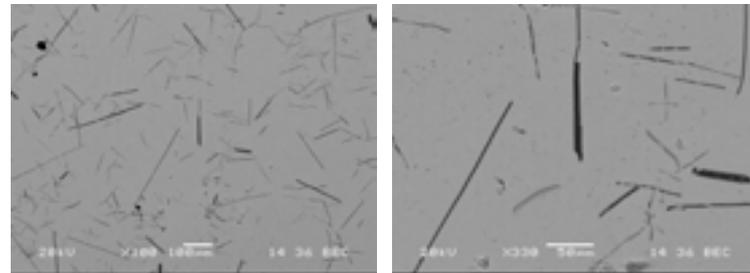

Ultra-low friction coatings for MEMS

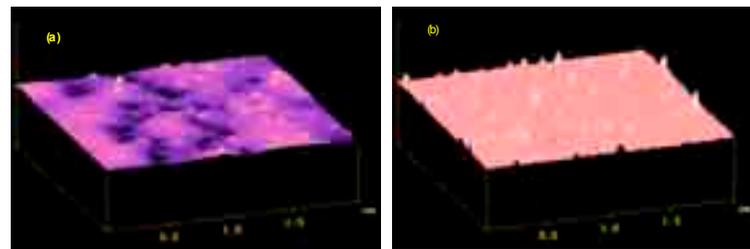

Friction-stir welding tips